



PROPERTIES OF SILK FABRIC DYED WITH EUCALYPTUS, QUERCETIN, RUTIN AND TANNIN USING PADDING TECHNIQUES

Rattanaphol Mongkhorrattanasit^{1,a*}, Nattaya Punrattanasin^{2,b}

^a*Department of Textile Chemistry Technology, Faculty of Industrial Textiles and Fashion Design, Rajamangala University of Technology Phra Nakhon, 517, Nakhonsawan Road, Kwang Suan Chitladda, Dusit District, Bangkok, 10300, Thailand*

²*Department of Textile Science and Technology, Faculty of Science and Technology, Thammasat University, Rangsit Center, Pathum Thani, 12121, Thailand*
rattanaphol.m@rmutp.ac.th¹, pnattaya@tu.ac.th²

Abstract: Natural dyes from eucalyptus leaf extract, quercetin, rutin and tannin were applied to silk fabric by the padding techniques, namely the pad-batch and pad-dry techniques under different condition. In this experiment, ferrous sulfate was used as a mordant. The dyeing properties were evaluated by measuring *K/S* values and *CIELAB*. The different fastness properties were evaluated. The effect of dyes at different concentration levels with respect to their colour strength was also studied.

Keywords: natural dyes, eucalyptus, quercetin, rutin, tannin, pad-batch, silk, dyeing

1. Introduction

Natural dyes are known for their use in colouring of food substrate, leather, wood as well as natural fibers like wool, silk, cotton and flax as major areas of application since ancient times. Natural dyes may have a wide range of shades, and can be obtained from various parts of plants including roots, bark, leaves, flowers, and fruit [1]. Dyeing with natural dyes, however, normally requires the use of mordants, which are metallic salts of aluminum, iron, chromium, copper, among others, for ensuring a reasonable fastness of the colour to sunlight and washing [2]. The metal ions of these mordants can act as electron acceptors for electron donors to form coordination bonds with the dye molecules, making them insoluble in water. Lately, there has been increasing interest in natural dyes, as the public is becoming more aware of the ecological and environmental problems related to the use of synthetic dyes. The use of natural dyes cuts down significantly on the amount of toxic effluent resulting from synthetic dye processes. Natural dyes have also been used for antimicrobial [3-7] and for printing [8 - 11]. It is reported that some natural (vegetable) dyes not only dye with unique and elegant colours, but they also provide antibacterial and UV protective functions to fabrics [12-15]. Thus, these natural dyes are applied on fibres or fabrics of cotton, wool, silk, and flax.

Eucalyptus is one of the most important sources of natural dye that gives yellowish-brown colourants. The colouring substance of eucalyptus has ample natural tannins and polyphenols varying from 10% to 12% [16]. The major colouring component of eucalyptus bark is quercetin, which is also an antioxidant. It has been used as a food dye with high antioxidant properties [17]. Eucalyptus leaves contain up to 11% of the major components of tannin (gallic acid and ellagic acid) and flavonoids (quercetin, and rutin, etc.) as minor substances [18-20]. Tannins and flavonoids are considered very useful substances during the dyeing process because of their ability to fix dyes within fabrics. The structures of selected important colouring components of eucalyptus leaves are given in Figure 1.

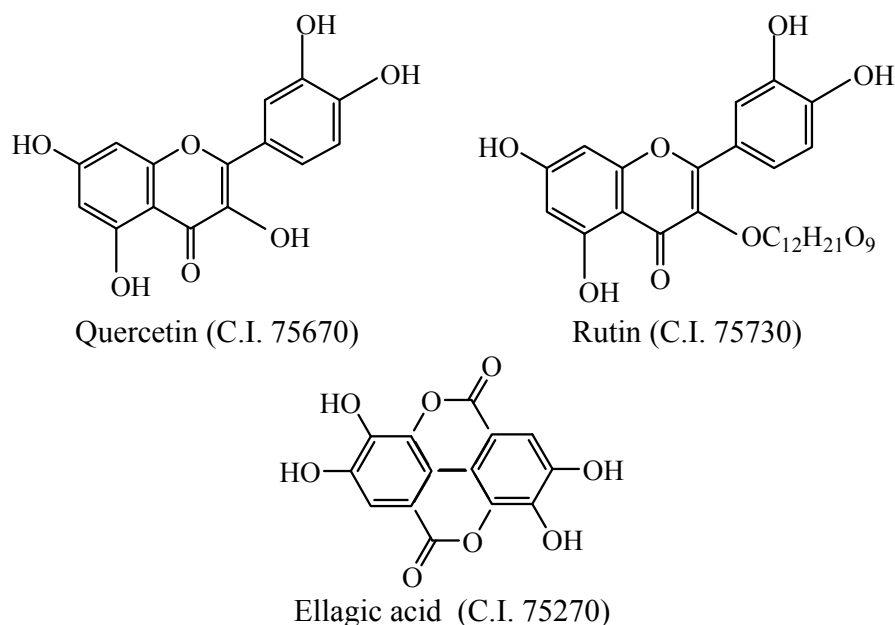


Figure 1. Colour composition of eucalyptus leaf extract dye.

Vegetable tannin extracts contain a variety of amorphous materials including polyphenolic tannins of large relative molecular mass (M_r), such as hydrolysable gallotannin, and tannic acid, as well as a less-complex of non-tannins, such as flavones and gums [21]. Because tannins have a large M_r and are water-soluble phenolic compounds, they undergo typical phenolic reactions, notably the chelation of metal ions. Tannins have been used in textiles for several hundreds of years, as exemplified by the dyeing of cotton and silk with dyewoods, in which the tannin is 'fixed' by a metal salt (e.g., CuSO_4) employed as a mordant for the dye [22]. Perkin [23] used tannins as mordants to increase the uptake of cationic dyes (e.g., Mauvein) onto cotton by firstly applying tannin to the cotton, followed by the 'fixing' of tannin by the application of metal (Fe, Al, Cu, Pb, or Sn) salt.

Flavonoids (polyphenolic pigments) are widely present in plants. Rutin (3,3',4',5,7-pentahydroxyflavone-3-rhamnoglucoside) and quercetin (3,3',4',5,7-pentahydroxyl-flavone) are phenolic compounds derived from hydroxyl substitutions on a flavone chromophore. Flavone-based compounds are known to form stable complexes with metal cations (Fe, Cu, Al and Cr) [24]. Flavonoids and tannins are two of the most interesting natural phenolic compounds.

Our interest lies in the colour that these compounds impart when added to silk fabric by the pad-batch dyeing technique, whereby a cloth is "padded" mechanically, applied by rapid passage through a small padding trough, followed by intensive squeezing between expression rollers and then dye fixation by batch at room temperature. After the dye fixation, the samples are thoroughly rinsed and air-dried.

Pure quercetin, rutin, and tannin were used in this study because they are the most common and effective. They are abundant in eucalyptus leaves. $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$ mordant was also used in this work. This study also investigated the *CIELAB* and *K/S* values of the dyeing, as well as the fastness properties.



2. Experimental

2.1 Materials and chemicals

The eucalyptus leaves (*Eucalyptus camaldulensis*) used in this study were collected in Thailand. Quercetin dehydrate, 98% purity ($C_{15}H_{10}O_7 \cdot 2H_2O$, $M_w = 338.80$), rutin hydrate, 95% purity ($C_{27}H_{30}O_{16} \cdot xH_2O$, $M_w = 610.52$), and tannin Ph. Eur. 5 ($C_{76}H_{52}O_{46}$, $M_w = 1701.20$) were purchased from Sigma, Fluka and Lachner, respectively. A commercially produced plain-weave silk fabric (thickness 0.15 mm, weight 67 g/m², fabric count per inch 96 x 80) was scoured and bleached (supplied by Chul Thai Silk Co., Thailand). The mordant used was ferrous (II) sulfate heptahydrate ($FeSO_4 \cdot 7H_2O$). The anion wetting agent - Altaran S8 (Sodium alkylsulfate) and soaping agent- Syntapon ABA were supplied by Chemotex Děčín, Czech Republic.

2.2 Instrumentation

The mordanting and dyeing were carried out in a two-bowl padding mangle machine (Mathis, type number HVF.69805). A spectrophotometer (Datacolor 3890) was used to measure the colour strength. The colour strength, in terms of K/S values, was calculated using the Kubelka-Munk equation, $K/S = (1-R)^2/2R$, where R is reflectance of the dyed fabric; K is the sorption coefficient, and S is the scattering coefficient.

2.3 Dye extraction from eucalyptus leaves

Fresh eucalyptus leaves (*Eucalyptus camaldulensis*) were dried in sunlight for one month and crumbled using a blender and then were used as the raw material for dye extraction, which was achieved by the reflux technique: 70 g of crumbled eucalyptus leaves was mixed with 1 l of distilled water and refluxed for 1 h. It was then filtered and the dye solution was separated into two parts: (a) one for evaporating under reduced pressure (rotary evaporator), and (b) one for dyeing. The rotary evaporator provided a crude dye extract of eucalyptus leaves. Then, it was crumbled with a blender and used for obtaining the standard calibration curve. The dilution of the eucalyptus leaf extract gives a relatively clear solution system with a linear dependence on the concentration absorbance, an absorption peak (λ_{max}) at 262 nm [26]. The concentration of 20 g/l was calculated from a standard curve of concentrations of the eucalyptus leaf extract dye solution versus absorbance at the wavelength mentioned.

2.4 Mordanting and pad-dyeing

A simultaneous padding process was used in this study. To study the effect of dye concentration, three concentrations of the eucalyptus leaf extract, quercetin, rutin, and tannin dyes were chosen: 1 and 5 g/L. Ferrous sulfate mordant was used at concentration of 5 g/L for each dye concentration and 1 g/L of an anionic wetting agent (Altaran S8) was added to the dye solution. The pH of the dyeing solution (mixed with an acetic acid solution) was adjusted to 4. This pH condition has been optimised in the previous study [15, 27-28]. The fabric was then immersed in the dye solution at room temperature and padded on a two-bowl padding mangle at 80% pick up. After padding for 2 seconds, the samples were dried at 90 °C for 3 min for the pad-dry technique. Under the cold pad-batch dyeing technique, the padded fabric was rolled on a glass rod with a plastic sheet wrapped around the rolled fabric. Then, it was kept at room temperature for 24 hours. The samples were then washed in 1 g/L of the soaping agent, Syntapon ABA, at 80 °C for 5 min and air-dried at room temperature.



2.5 Evaluation of colour strength and fastness properties











The colour strength (K/S) and $CIELAB$ of the dyed samples were evaluated using a spectrophotometer (Datacolor 3890). All samples measured showed a λ_{max} value of 400 nm. The colour fastness to washing, light and rubbing of the dyed samples was determined according to ISO 105-C06 A1S: 1994, ISO 105-B02: 1994, and ISO 105-X12: 2001, respectively.

3. Results and discussion







3.1 Effect of dyeing on CIELAB and K/S values

The colour value results are presented in Tables 1 and 2. Silk fabric dyed with eucalyptus leaf extract and tannin dye showed a pale yellowish-grey shade, while those dyed with ferrous sulfate showed a dark greyish-brown colour. Silk fabric dyed with quercetin without a mordant had a yellowish green colour. Silk mordanted with ferrous sulfate produced a dark yellowish-brown shade. Silk substrates dyed with rutin gave a pale yellowish-green, while those dyed with ferrous sulfate had a yellowish-brown colour.

Table 1 Colour value of silk fabric dyed with eucalyptus leaf extract and quercetin dyes by using simultaneous mordanting and padding techniques









Type of dye	Concentration	Pad-batch					Pad-dry				
		K/S	L^*	a^*	b^*	Dyed Sample	K/S	L^*	a^*	b^*	Dyed sample
Eucalyptus	1 g/L Dye (without mordant)	0.59	86.5	2.0	-3.6		0.58	86.4	2.1	-3.8	
	5 g/L Dye (without mordant)	0.71	85.8	1.4	-1.4		0.66	86.2	1.5	-1.2	
	1 g/L Dye + 5 g/L FeSO ₄	1.54	56.9	2.1	-1.8		1.48	60.9	2.3	-1.6	
	5 g/L Dye + 5 g/L FeSO ₄	1.75	69.1	2.4	-1.2		1.63	58.2	1.9	-1.1	
Quercetin	1 g/L Dye (without mordant)	1.17	85.4	-2.2	6.0		1.09	86.3	-1.6	5.1	











5 g/L Dye (without mordant)	1.58	86.3	-3.4	10.2		1.38	87.0	-3.0	8.2	
1 g/L Dye + 5 g/L FeSO ₄	4.55	46.9	3.5	20.1		4.30	51.9	1.7	15.2	
5 g/L Dye + 5 g/L FeSO ₄	8.03	36.7	1.4	14.9		7.61	39.8	2.9	16.8	

From Tables 1 and 2, it is clear that the colour shade of the fabrics dyed with tannin (a major constituent of eucalyptus leaves) is colourimetrically and visually observed to be very similar to that using eucalyptus leaf extract dye. The colours obtained with the various dyes vary in their tone due to the fact that when the different dyes (eucalyptus leaf extract, quercetin, rutin, and tannin) are combined with ferrous sulfate to form dye-ferrous complexes, different shades are then attained.

Table 2 Colour value of silk fabric dyed with rutin and tannin dyes by using simultaneous mordanting and padding techniques

Type of dye	Concentration	Pad-batch				Dyed Sample	Pad-dry				Dyed sample
		K/S	L*	a*	b*		K/S	L*	a*	b*	
Rutin	1 g/L Dye (without mordant)	0.71	87.5	0.05	0.1		0.65	87.4	0.8	-1.6	
	5 g/L Dye (without mordant)	0.83	86.1	-0.4	2.0		0.76	87.0	-0.1	1.1	
	1 g/L Dye + 5 g/L FeSO ₄	4.10	60.1	1.5	20.0		2.30	69.4	3.3	19.7	
	5 g/L Dye + 5 g/L FeSO ₄	4.73	56.4	1.2	19.2		3.00	63.1	2.3	19.0	



Tannin	1 g/L Dye (without mordat)	0.58	86.2	2.0	-3.4		0.56	86.7	2.4	-4.1	
	5 g/L Dye (without mordat)	0.78	84.7	0.9	-1.0		0.67	86.8	1.3	-1.0	
	1 g/L Dye + 5 g/L FeSO ₄	2.04	53.0	2.3	-1.8		1.77	54.5	2.1	-2.1	
	5 g/L Dye + 5 g/L FeSO ₄	2.96	40.1	2.9	-4.4		2.81	41.6	4.1	-6.4	

Figures 2 and 3 show the colour strength (K/S) values of silk fabric dyed with eucalyptus leaf extract, quercetin, rutin and tannin, respectively. It can be observed that the K/S values increase with an increase in dye concentrations. Silk fabric dyeing by pad-batch technique showed higher K/S values than using the pad-dry technique.

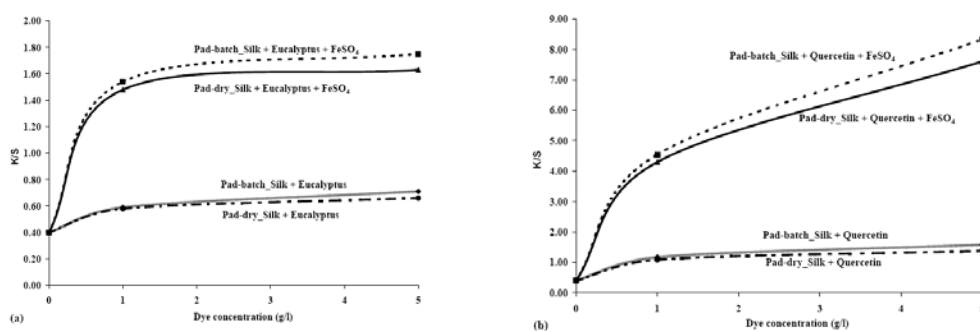


Figure 2. K/S values of silk fabric dyed with 1 g/L and 5 g/L ; eucalyptus leaf extract dye solutions (a) and quercetin (b) with 5 g/L FeSO₄, using pad-batch and pad-dry techniques

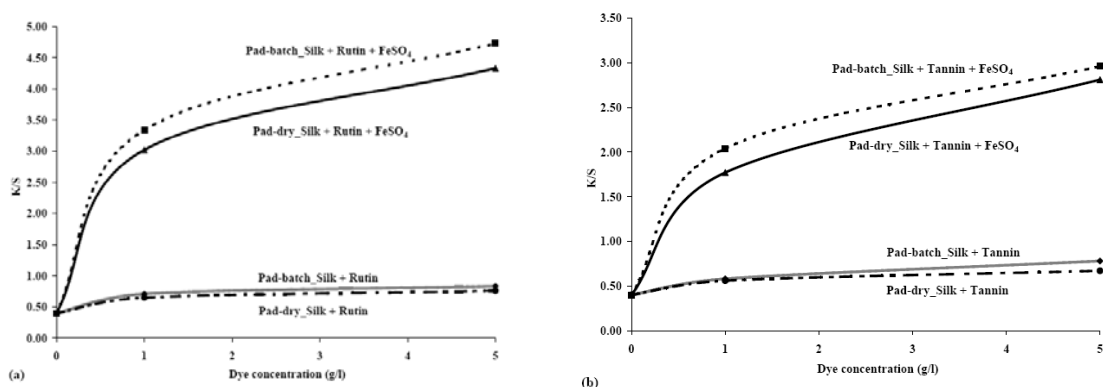


Figure 3. *K/S* values of silk fabric dyed with 1 g/L and 5 g/L ; rutin (a) and tannin (b) with 5 g/L FeSO₄, using pad-batch and pad-dry techniques

It can be concluded that silk fabrics can be successfully dyed with eucalyptus leaf extract dye, quercetin, rutin and tannin due to the formation of ferrous coordination complexes. Ferrous sulfate readily chelated with the dyes. As the coordination number of ferrous sulfate is 6, some coordination sites remain unoccupied when they interact with the fiber, which allows functional groups, such as amino and carboxylic acid, on the fiber to occupy these unoccupied sites. Thus ferrous can form a ternary complex on one site with the fiber and on another site with the dye [29].

3.2 The colour fastness properties

The fastness ratings of silk fabric dyed with and without mordants at a dye concentration of 5 g/L and ferrous sulfate (5 g/L) are presented in Tables 3 to 5. Table 3 indicates that the washing fastness rating of silk fabric dyed with eucalyptus leaf extract, quercetin, rutin and tannin is very good (4 to 4-5). A probable explanation for the good fastness property is that tannin and flavonoids (quercetin and rutin) can form metal chelates with the ferrous mordant. Hence, after mordanting, the tannin and flavonoids are insoluble in water, thereby ultimately improving the washing fastness.



Table 3. Colour fastness to washing at 40°C (ISO 105-C06 A1S: 1994)

Dyeing and mordanting conditions	Colour change	Colour staining of multifibers					
		Acetate	Cotton	Nylon	Polyester	Acrylic	Wool
Pad-batch							
Eucalyptus	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Eucalyptus + Fe	4	4-5	4	4-5	4-5	4-5	4
Quercetin	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Quercetin + Fe	4	4-5	4	4	4-5	4-5	4
Rutin	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Rutin + Fe	4	4-5	4-5	4-5	4-5	4-5	4-5
Tannin	4-5	4-5	4-5	4-5	4-5	4-5	4
Tannin + Fe	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Pad-dry							
Eucalyptus	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Eucalyptus + Fe	4	4-5	4-5	4-5	4-5	4-5	4
Quercetin	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Quercetin + Fe	4	4-5	4	4-5	4-5	4-5	4-5
Rutin	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Rutin + Fe	4	4-5	4	4-5	4-5	4-5	4-5
Tannin	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Tannin + Fe	4	4-5	4	4-5	4-5	4-5	4

Note: Fe = FeSO₄

As seen in Table 4, a light fastness in the range of 3-4 (fair) can be observed in the silk fabric, except for that dyed with quercetin without mordant, whose rating was 2 (poor). This is attributed to the fact that the presence of 3-hydroxy groups in quercetin reduces the light fastness due to lower photostability [30]. However, silk dyed with tannin with or without a mordant, which shows to be in the range of 4 to 4-5 (good).

Table 4. Colour fastness to light (ISO 105-B02: 1994)

Dyeing and mordanting conditions	Colour change	
	Pad-batch	Pad-dry
Eucalyptus	3-4	3-4
Eucalyptus + FeSO ₄	3-4	3-4
Quercetin	2	2
Quercetin + FeSO ₄	3-4	3-4
Rutin	3	3
Rutin + FeSO ₄	3-4	3-4
Tannin	4	4
Tannin + FeSO ₄	4-5	4-5

From Table 5, very good (4-5) rubbing fastness can be observed in silk fabric dyed with eucalyptus leaf extract, quercetin, rutin and tannin, except for those mordanted with ferrous sulfate, whose ratings were 3 to 4 (fair to good). However, the fabrics dyed with eucalyptus, tannin and ferrous sulfate show a rating of 2 to 3 (poor to fair). This is attributed to a difference in the extent to which the low aqueous solubility ferrous-tannate complexes were able to diffuse within the dyed fiber. For the large molecular size complex that was formed within the dyeing bath, it could be anticipated to display very low diffusional behaviour and, therefore, to deposit mostly on the periphery of the dyed fiber, resulting in a low rubbing fastness [21].



Table 5. Colour fastness to rubbing (ISO105- X12: 2001)

Dyeing and mordanting conditions	Pad-batch				Pad-dry			
	Warp direction		Weft direction		Warp direction		Weft direction	
	Colour staining		Colour staining		Colour staining		Colour staining	
	Dry	Wet	Dry	Wet	Dry	Wet	Dry	Wet
Eucalyptus	4-5	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Eucalyptus + Fe	3	2-3	3	2-3	3	2-3	3	2-3
Quercetin	4-5	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Quercetin + Fe	3-4	3-4	3-4	3-4	3-4	3-4	4	3-4
Rutin	4-5	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Rutin + Fe	4	4	4	4	4	4	4	4
Tannin	4-5	4-5	4-5	4-5	4-5	4-5	4-5	4-5
Tannin + Fe	3	2-3	3	2-3	3	2-3	3	2-3

Note: Fe = FeSO₄

4. Conclusions

Silk fabrics dyed with eucalyptus leaf extract, quercetin, rutin and tannin by using pad-batch show higher colour strength than pad-dry technique. Tannins are considered as a main material in dyeing processes not only because of the shade similarities of eucalyptus leaves and tannin dyed on silk fabric. The colour fastness to washing shows very good results, whereas the colour fastness to rubbing was fair to good, except for silk fabric dyed with tannin and eucalyptus with ferrous sulfate as the mordant, whose rating was poor when subjected to wet rubbing. The light fastness property of the silk fabric mordanted with ferrous sulfate shows a fair to good result, but in the case of the silk fabric dyed with quercetin without mordant, whose rating was poor fastness. The application of natural dyes on silk fabric by the pad-dry technique can be considered to be an effective eco- option; hence the technique could be considered to be the most suitable for small scale industries or for the cottage dyeing of natural dyes.

References

- [1] Allen, R. L. M.: *Colour chemistry*, Nelson, London, 1971, ISBN 978-0-177-61717-1.
- [2] Robertson S. M.: *Dyes from Plants*, Van Nostrand Reinhold, New York: 1973, ISBN 978-0442269746.
- [3] Singh, R.; Jain, A; Panwar, S.; Gupta, D. & Khare, S. K.: Antimicrobial activity of some natural dyes, *Dyes and Pigments*, Vol. 66 (2005) No. 2, pp. 99-102, ISSN 0143-7208.
- [4] Sarkar, A. K. & Dhandapani, R.: Study of natural colorants as antibacterial agents on natural fibers, *Journal of Natural Fibers*, Vol. 6 (2009) No. 1, pp. 46–55, ISSN 1544-0478.
- [5] Hang, S. & Yang, Y.: Antimicrobial activity of wool fabric treated with curcumin. *Dyes and Pigments*, Vol. 64 (2005) No.2: pp. 157-161, ISSN 0143-7208.
- [6] Dahl, T. A. McGowan, W. M.; Shand, M. A. & Srinivasan, V. S.: Photokilling of bacteria by the natural dye curcumin. *Archives of Microbiology*, Vol. 151 (1989) No.2, pp. 183-185, ISSN 1432-072X.
- [7] Khan, M. R.; Omoloso, A. D. & Kihara, M.: Antibacterial activity of *Artocarpus heterophyllus*. *Fitoterapia*, Vol. 74 (2003) No. 5, pp. 501-505, ISSN 0367-326X.



- [8] Rekaby, M.; Salem, A. A.; & Nassar, S. H.: Eco-friendly of natural fabrics using natural dyes from alkanet and rhubarb, *The Journal of The Textile Institute*, Vol. 100 (2009) No.6, pp. 486-495, ISSN 1754-2340.
- [9] Karolia, A. & Buch, H.: *Ajarkh*, the resist printed fabric of Gujarat, *Indian Journal of Traditional Knowledge*. Vol. 7 (2008) No.1, pp. 93-97, ISSN 0975-1068.
- [10] Hebeish, A. A.; Ragheb, A. A.; Nassar, S. H.; Allam, E. E.; El Thalouth, J. I. A.: Technological evaluation of reactive cyclodextrin in cotton printing with reactive and natural dyes, *Journal of Applied Polymers Science*, Vol.102 (2006) No.1, pp. 338-347, ISSN 1097-4628.
- [11] Hakeim, O. A.; Abou-Okeil, A.; Abdob, L. A. W. & Waly, A.: The influence of chitosan and some of its depolymerized grades on natural colour printing, *Journal of Applied Polymers Science*, Vol. 97 (2005) No.2, pp. 559-563, ISSN 1097-4628.
- [12] Kim, S.: Dyeing characteristic and UV protection property of green tea dyed cotton fabrics. Focusing on the effect of chitosan mordanting condition, *Fibers and Polymers*, Vol. 7 (2006) No. 3, pp. 255-261, ISSN 1875-0052.
- [13] Feng, X.X.; Zhang, L. L.; Chen, J. Y.; & Zhang, J. C.: New insights into solar UV-protectives of natural dye, *Journal of Cleaner Production*, Vol. 15 (2007) No. 4, pp. 366-372, ISSN 0959-6526.
- [14] Sarkar, A.K.: An evaluation of UV protection imparted by cotton fabric dyed with natural colorants, *BMC Dermatology*, Vol. 4 (2004) No. 15, pp. 1-8, ISBN 1471-5945.
- [15] Mongkhohattanasit, R.; Kryštůfek, J.; Wiener, J. & Víková, M.: UV protection property of silk fabric dyed with eucalyptus leaf extract, *The Journal of The Textile Institute*, Vol. 102 (2011) No. 3, pp. 272-279, ISSN 1754-2340.
- [16] Ali, S.; Nisar, N. & Hussain, T.: Dyeing properties of natural dyes extracted from eucalyptus, *The Journal of The Textile Institute*, 98 (2007) No.6, pp.559-562, ISSN 1754-2340.
- [17] Vankar, P. S.; Tiwari, V. & Srivastava, J.: Extracts of steam bark of *Eucalyptus Globules* as food dye with high antioxidant properties, *Electronic Journal of Environmental, Agricultural and Food Chemistry*, 5 (2006) No.6, pp. 1664-1669, ISSN 1579-4377.
- [18] Chapuis-Lardy, L.; Contour-Ansel, D. & Bernhard-Reversat, F.: High performance liquid chromatography of water-soluble phenolics in leaf litter of three eucalyptus hybrids (Congo), *Plant Science*, Vol. 163 (2002) No.2, pp. 217-222, ISSN 0168-9452.
- [19] Conde, E.; Cadahia, E. & Garcia-Vallejo, M. C.: Low molecular weight polyphenols in leaves of *Eucalyptus camaldulensis*. *E. globules* and *E. rudis*, *Phytochemical Analysis*, Vol. 8 (1997) No.4, pp. 186-193, ISSN 1099-1565.
- [20] Conde, E.; Cadahia, E.; Garcia-Vallejo, M. C. & Fernandez de Simon, B.: High pressure liquid chromatographic analysis of polyphenols in leaves of *Eucalyptus camaldulensis*. *E. globules* and *E. rudis*: proanthocyanidins, ellagitannins and flavonol glycosides, *Phytochemical Analysis*, 8 (1997) No.2, pp. 78-83, ISSN 1099-1565.
- [21] Burkinshaw, S. M. & Kumar, N.: A tannic acid/ ferrous sulfate aftertreatment for dyed nylon 6,6, *Dyes and Pigments*, Vol. 79 (2008) No.1, pp. 48-53, ISSN 0143-7208.
- [22] Burkinshaw, S. M. & Kumar, N.: The mordant dyeing of wool using tannic acid and FeSO₄, Part 1: Initial finding, *Dyes and Pigments*, Vol. 80 (2009) No.1, pp. 53-60, ISSN 0143-7208.
- [23] Burkinshaw, S. M.: *Chemical principles of synthetic fibre dyeing*, Chapman and Hall, Glasgow, 1995, ISBN 978-0-751-40043-4.



- [24] Septhum C.; Rattanaphani V. & Rattanaphani S.: UV-Vis spectroscopic study of natural dyes with alum as a mordant, *Suranaree Journal Science Technology*, Vol. 14 (January-March 2007) No.1 , pp. 91-97, ISSN 0858-849X.
- [26] Yarosh, E.A.; Gigoshvili, T.I. & Alaniya, M.D.: Chemical composition of eucalyptus jumanii cultivated in the humid Georgian subtropics, *Chemistry of Natural Compound*, Vol. 37 (2001) No.1, pp. 86-87, ISSN 1573-8388.
- [27] Mongkholrattanasit, R. & Vitidsant, T.: Dyeing and colour fastness properties of silk and cotton fabrics dyed with eucalyptus leaves extract. *6th International Conference TEXSCI*, Liberec, Czech Republic. (2007): pp. 285-286.
- [28] Mongkholrattanasit, R.; Wongphakdee, W. & Sirikasemlert, C.: Dyeing and colour fastness properties of silk and cotton fabrics dyed with eucalyptus bark extract. *RMUTP Research Journal*, Vol. 1 (2007) No.1, pp. 41-49, ISSN 1906-0432.
- [29] Bhattacharya, S. D.; Shah, A. K.: Metal ion effect on dyeing of wool fabric with catechu, *Coloration Technology*, Vol. 116 (2000) No. 1, pp. 10-12, ISSN 1478-4408.
- [30] Bhat, S. V.; Nagasampagi, B. A.; Sivakumar, M.: *Chemistry of natural products*, Narosa, New Delhi, 2006, ISBN 978-3-540-40669-3.